



APPLICATIONS OF NANOTECHNOLOGY IN PULP AND PAPER: ADVANCES, CHALLENGES, AND FUTURE PROSPECTS

Shwet Vashishtha

R.P.P.T. Laboratory, National Test House, Ghaziabad, India

ABSTRACT

The pulp and paper industry, producing over 400 million tons annually, faces challenges including limited mechanical strength, poor barrier properties, petroleum-based coatings, and high chemical use in pulping/bleaching. Nanotechnology offers transformative solutions via nanocellulose (CNCs, CNFs, BNC) for reinforcement, enhancing tensile strength, flexibility, and barrier resistance, alongside nanostructured coatings (TiO₂, SiO₂, ZnO, AgNPs, nanoclays) for hydrophobicity, antimicrobial activity, and gas/moisture barriers. Nano-catalysts and enzyme hybrids enable efficient, chlorine-reduced pulping/bleaching, while smart papers emerge for sensors, electronics, and filtration. This review evaluates these advances, industrial prospects (e.g., pilot-scale CNF/CNC), environmental/economic impacts (LCA, AOX reduction), and barriers (cost, toxicity, regulations). It charts a path to carbon-neutral, multifunctional papers, replacing plastics via mill-integrated nanotechnology.

KEYWORDS : Nanocellulose, Pulp and paper, Nanotechnology, Coatings, Barrier properties, Pulping, Sustainability

1. INTRODUCTION

The pulp and paper industry plays a vital role in global economies, supporting communication, education, and packaging sectors. However, the industry is energy-intensive, water-demanding, and heavily dependent on chemicals such as chlorine dioxide, sodium hydroxide, and hydrogen peroxide in pulping and bleaching [1]. However, conventional paper has inherent limitations—low tensile and tear strength, susceptibility to water absorption, and poor barrier resistance to gases and oils—that restrict its competitiveness against plastics and polymers [2].

The increasing demand for sustainable packaging solutions driven by regulations on single-use plastics has accelerated the search for advanced paper-based materials [3]. Nanotechnology offers potential solutions by introducing materials with tailored functionalities at the molecular or nanoscale level. Nanomaterials can enhance the intrinsic properties of paper fibers, modify surface characteristics, and provide new functional attributes such as antimicrobial activity, hydrophobicity, and electrical conductivity [4].

Nanocellulose—derived directly from lignocellulosic fibers—represents a biodegradable and renewable nanomaterial that aligns with circular economy and bioeconomy goals [5]. In parallel, inorganic nanoparticles such as TiO₂, ZnO, and AgNPs offer multifunctional coatings that improve printability, brightness, or antimicrobial performance [6]. These advances transform paper from a traditional commodity into a multifunctional material platform suitable for packaging, electronics, filtration, and biomedical applications.

This review presents a comprehensive analysis of nanotechnology applications in the pulp and paper industry, focusing on (i) nanocellulose applications, (ii) nanostructured coatings and fillers, (iii) nanotechnology in pulping and bleaching, (iv) smart and functional papers, (v) environmental and economic impacts, (vi) challenges, and (vii) future prospects. By integrating advances in materials science with industrial papermaking, nanotechnology provides a pathway towards sustainable and high-performance paper products. These challenges and their potential nanotechnology-based solutions are summarized in Figure 1.

2. Nanocellulose in Paper and Pulp

Nanocellulose is the most extensively studied nanomaterial in the pulp and paper sector because it originates from cellulose—the primary constituent of pulp fibers. It can be classified into three main forms: cellulose nanocrystals (CNCs), cellulose nanofibrils (CNFs), and bacterial nanocellulose (BNC) [12].

2.1 Cellulose Nanocrystals (CNCs)

CNCs are rod-like nanoparticles (length: 100–300 nm; diameter: 5–20 nm) typically obtained by acid hydrolysis of cellulose fibers [13]. Their high crystallinity (60–90%) and aspect ratio make them excellent reinforcing agents in paper sheets. When incorporated into paper, CNCs improve tensile index, stiffness, and surface smoothness, while also enhancing barrier resistance to oxygen and grease [14]. CNC-based coatings are transparent and can replace petroleum-derived polymers in food packaging films [15].

2.2 Cellulose Nanofibrils (CNFs)

CNFs are long, flexible fibrils (length: several micrometers; diameter: 20–50 nm) obtained through mechanical fibrillation combined with enzymatic or TEMPO-mediated oxidation pretreatments [16]. They possess high aspect ratios and hydrogen-bonding capacity, enabling network formation with paper fibers. CNFs act as natural binders in paper sheets, improving folding endurance, tear index, and burst strength [17]. Their gel-like rheology also allows them to serve as barrier coatings, reducing water vapor transmission rates significantly [18].

2.3 Bacterial Nanocellulose (BNC)

BNC is produced extracellularly by bacteria such as *Komagataeibacter xylinus* under aerobic fermentation [19]. Unlike CNCs and CNFs, BNC is highly pure, free from lignin or hemicellulose, and exhibits a unique three-dimensional nanofiber network. It is used in high-value applications such as medical wound dressings, membranes, and filtration papers [20]. In the paper industry, BNC has potential as a reinforcement additive for specialty grades where exceptional barrier or mechanical properties are required [21].

The structural features and unique properties of CNC, CNF, and BNC are compared in Figure 1.

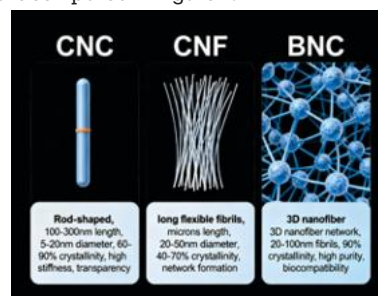


Figure 1: Comparison of Structural Features and Unique Properties of Cellulose Nanocrystals (CNC), Cellulose Nanofibrils (CNF), and Bacterial Nanocellulose (BNC)

2.4 Industrial Prospects of Nanocellulose

Pilot-scale and industrial initiatives are underway in North America, Europe, and Asia for large-scale CNF and CNC production [22]. Companies like CelluForce (Canada) and Stora Enso (Finland) have invested in CNC/CNF plants to commercialize nanocellulose for packaging and composites. However, energy-intensive production and high costs (>\$5000/ton) remain major barriers to mainstream adoption [23]. Research is focusing on integrating nanocellulose production into pulp mills using agro-residues (wheat straw, sugarcane bagasse) to lower costs and valorize waste streams [24]. Table 1 presents a comparative overview of cellulose nanocrystals (CNC), cellulose nanofibrils (CNF), and bacterial nanocellulose (BNC), highlighting their typical dimensions, crystallinity, key properties, and major applications in the pulp and paper industry.

Table 1. Comparative Properties of Different Nanocellulose Types

Nanocellulose Type	Typical Dimensions	Crystallinity (%)	Key Properties	Major Applications
CNC	100–300 nm length, 5–20 nm diameter	60–90	High stiffness, transparency, gas barrier	Packaging films, reinforcement, coatings
CNF	Microns in length, 20–50 nm diameter	40–70	Flexibility, network formation, gel rheology	Paper reinforcement, barrier coatings, composites
BNC	3D nanofiber network, 20–100 nm fibrils	>90	Purity, biocompatibility, high water-holding	Medical paper, filtration, specialty coatings

3. Nanostructured Coatings and Fillers

3.1 Hydrophobic and Oleophobic Coatings

Traditional paper is inherently hydrophilic due to the abundance of hydroxyl groups in cellulose, resulting in poor water and oil resistance. This limitation necessitates plastic or wax coatings for packaging, which compromise recyclability. Nanostructured coatings offer an eco-friendly alternative by imparting hydrophobicity and oleophobicity through surface modification at the nanoscale.

Silica (SiO₂) nanoparticles are widely studied for creating superhydrophobic paper surfaces via the lotus-leaf effect [7]. When combined with low-surface-energy compounds (e.g., fluorosilanes, fatty acids), SiO₂-coated paper achieves water contact angles exceeding 150°, significantly reducing liquid absorption. Similar strategies using zinc oxide (ZnO) and titanium dioxide (TiO₂) nanoparticles have demonstrated enhanced wet strength and moisture resistance [8]. Recent studies report that incorporating graphene oxide nanosheets into coating formulations further improves water repellency while maintaining gas permeability [9].

Oleophobic properties are particularly relevant for food packaging. Nanoclay platelets and fluorinated nanoparticles form barrier layers against oils and greases, reducing Cobb values by 40–60% compared to uncoated papers [10]. Such coatings provide a sustainable alternative to polyethylene-laminated paperboard.

3.2 Antimicrobial Coatings

The COVID-19 pandemic renewed interest in antimicrobial packaging and hygienic papers. Metallic nanoparticles such as silver (AgNPs), zinc oxide (ZnO), and copper oxide (CuO) exhibit strong antimicrobial activity by generating reactive oxygen species and disrupting microbial membranes [11].

AgNP-coated papers are effective against E. coli and S. aureus, making them suitable for food wrapping and medical packaging [12].

TiO₂ nanoparticles also provide photocatalytic sterilization when exposed to UV light, continuously degrading microbial contaminants [13]. Recent hybrid systems combine nanocellulose films with AgNPs or ZnO to provide controlled ion release, offering prolonged antimicrobial functionality [14]. Regulatory challenges remain concerning nanoparticle migration into food, but encapsulation techniques are being developed to minimize risks [15].

3.3 Gas and Moisture Barrier Coatings

The packaging industry demands materials with low oxygen transmission rates (OTR) and water vapor transmission rates (WVTR). Nanocoatings significantly enhance barrier performance by increasing the tortuosity of diffusion pathways. Nanoclays (e.g., montmorillonite) and layered double hydroxides (LDH) are incorporated into paper coatings to form impermeable structures that slow gas permeation [16].

Studies demonstrate that CNF–nanoclay composites reduce OTR by up to 90% compared to base paper, enabling applications in modified atmosphere packaging [17]. Similarly, TiO₂ and SiO₂ coatings improve moisture resistance, critical for protecting hygroscopic products. These nanostructured barriers could gradually replace multilayer laminates of polyethylene and aluminum foil, promoting recyclability [18].

3.4 Optical and Printability Enhancements

In addition to barrier functions, nanofillers improve the optical and printing quality of paper. TiO₂ nanoparticles are widely used to increase brightness and opacity due to their high refractive index [19]. Nano-CaCO₃ fillers improve smoothness, ink absorption, and reduce scattering, enhancing print clarity [20].

Graphene oxide and CNT-based coatings impart conductive pathways for printed electronics, expanding paper's application as a low-cost substrate for RFID tags, flexible circuits, and sensors [21].

Nanostructured coatings and fillers impart multiple functional properties to paper substrates, enhancing their hydrophobicity, antimicrobial activity, gas barrier capabilities, printability, and electrical conductivity. These multifunctional applications enable paper to compete with plastics in packaging, extend uses into printed electronics, and improve packaging performance with eco-friendly, high-performance coatings as summarized in Figure 2.

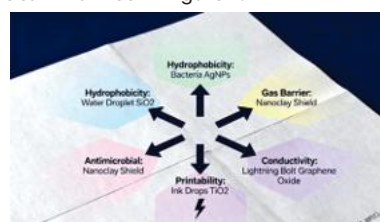


Figure 2: Multifunctional Applications of Nanostructured Coatings and Fillers in Paper:

The multifunctional roles of various nanostructured coatings and fillers in paper enhancement are summarized in Table 2, detailing their functions, performance improvements, and applicable paper-based products.

Table 2. Applications of Nanostructured Coatings and Fillers in Paper

Nanomaterial	Function	Performance improvement	Applications
--------------	----------	-------------------------	--------------

SiO ₂ nanoparticles	Hydrophobic coating	Water contact angle >150°	Water-resistant packaging
Nanoclay (montmorillonite)	Gas barrier	90% reduction in OTR	Food packaging films
AgNPs	Antimicrobial	Inhibits E. coli, S. aureus	Food/medical packaging
TiO ₂ nanoparticles	Brightness/UV protection	+15% ISO brightness	Printing & archival paper
Graphene oxide	Conductive coating	Electrical conductivity ~10 ⁻³ S/cm	Printed electronics, RFID

4. Nanotechnology in Pulping and Bleaching

The pulping and bleaching stages are critical in papermaking but are also the most resource- and chemical-intensive. Conventional kraft pulping generates large volumes of black liquor, while chemical bleaching with chlorine dioxide or hydrogen peroxide consumes high amounts of energy and chemicals, raising concerns about environmental emissions and cost [22]. Nanotechnology offers promising interventions through nanocatalysts, enzyme-nanoparticle hybrids, and advanced separation techniques that can reduce chemical use, improve pulp quality, and enhance process efficiency.

4.1 Nanocatalysts in Pulping

Nanocatalysts such as TiO₂, ZnO, and Fe₃O₄ nanoparticles have been employed to accelerate delignification and improve fiber liberation. Their high surface area-to-volume ratio and photocatalytic activity enable selective oxidation of lignin without excessive cellulose degradation [23].

- TiO₂ photocatalysts activated under UV light facilitate lignin breakdown and improve brightness by up to 20% ISO compared to conventional bleaching [24].
- Magnetic Fe₃O₄ nanoparticles act as reusable catalysts; after reaction, they can be separated from pulping liquor using magnetic fields, reducing secondary waste [25].
- ZnO nanoparticles exhibit catalytic synergy with hydrogen peroxide, enhancing oxidative bleaching and lowering chemical dosage by ~30% [26].

Nanocatalysts such as TiO₂, ZnO, and Fe₃O₄ nanoparticles accelerate delignification through selective lignin oxidation while enabling catalyst recovery. Figure 3 illustrates the complete process flow of nanocatalyst-assisted pulping and bleaching, showing pulp input, nanocatalyst addition, lignin oxidation under UV/magnetic activation, catalyst separation/recovery loop, and output of brightened pulp with minimal chemical waste.

Nanocatalyst-Assisted Pulping and Bleaching Process

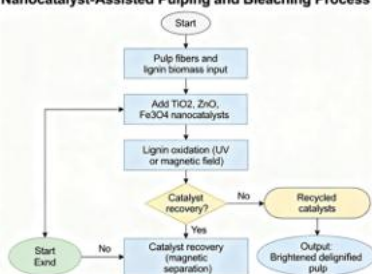


Figure 3: Flowchart of Nanocatalyst-assisted Pulping and Bleaching, Showing Lignin Oxidation and Catalyst Recovery.

4.2 Enzyme-Nanoparticle Hybrids

Enzymatic biobleaching is attractive due to its eco-friendliness, but enzymes are often unstable under industrial conditions. Immobilizing enzymes such as xylanases, laccases, or peroxidases on nanocarriers (e.g., silica nanoparticles, magnetic nanoparticles, or carbon nanotubes)

increases their thermal stability, reusability, and activity [27].

- Laccase-nanoparticle conjugates have been shown to reduce kappa number by 15–20%, improving bleachability of kraft pulp [28].
- Xylanase immobilized on magnetic nanoparticles enhances delignification, with >80% recovery of enzymatic activity after five reuse cycles [29].
- Nanocellulose-based supports are emerging as biocompatible carriers for enzyme immobilization, aligning with circular bioeconomy goals [30].

4.3 Nanofiltration and Membrane Applications

The recovery of chemicals and water from pulping effluents is another area where nanotechnology plays a role. Nanofiltration (NF) and ultrafiltration (UF) membranes enhanced with TiO₂, graphene oxide, or SiO₂ nanoparticles show improved permeability, fouling resistance, and selectivity [31].

- NF membranes with TiO₂ coatings demonstrated 40% higher black liquor recovery efficiency compared to unmodified membranes [32].
- Graphene oxide membranes exhibit high selectivity for lignin removal while allowing alkali recovery [33].
- Nanofiltration of bleach plant effluents reduces AOX (adsorbable organic halides) levels by 60–70%, contributing to lower environmental impact [34].

Nanofiltration (NF) membranes enhanced with nanoparticles such as TiO₂, graphene oxide, and SiO₂ demonstrate superior performance in pulp mill effluent treatment. These advanced membranes achieve 40% higher black liquor recovery efficiency, selective lignin removal while preserving alkali recovery, and 60-70% reduction in AOX levels from bleach plant effluents. Figure 4 illustrates the schematic process showing pulp mill wastewater input, nanoparticle-enhanced NF membrane separation, black liquor concentrates recovery stream, and clean water permeate for recycling back into mill operations.

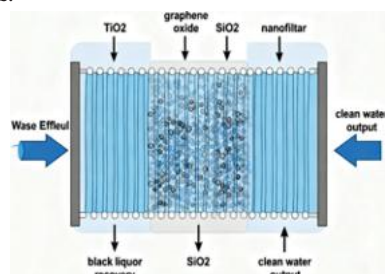


Figure 4: Schematic of Nanofiltration Membranes Used in Pulp Mill Effluent Recycling and Black Liquor Recovery.

4.4 Advantages and Industrial Implications

Integrating nanotechnology in pulping and bleaching offers multiple advantages:

- Reduced chemical load (20–30% reduction in ClO₂ or H₂O₂ consumption).
- Improved pulp brightness and strength properties.
- Lower environmental emissions, especially AOX and COD in effluents.
- Catalyst/enzyme recyclability, minimizing costs and waste.

However, industrial application is still limited to pilot-scale demonstrations due to the high cost of nanocatalysts and concerns about nanoparticle release into process streams [35].

Key nanomaterials employed in pulping and bleaching processes, along with their functions, performance improvements, and stages of industrial application, are outlined in Table 3.

Table 3. Nanotechnology Applications in Pulping and Bleaching

Nanomaterial/ Approach	Function	Performance Improvement	Industrial Status
TiO ₂ nanoparticles	Photocatalyst for lignin oxidation	+20% ISO brightness	Pilot-scale
Fe ₃ O ₄ nanoparticles	Magnetic nanocatalyst	Easy recovery & reuse	Lab-scale
ZnO nanoparticles + H ₂ O ₂	Oxidative bleaching catalyst	30% less peroxide use	Pilot-scale
Laccase-NP conjugates	Biobleaching	15–20% kappa number reduction	Lab-scale
Graphene oxide NF membranes	Black liquor recovery	40% higher efficiency	Pilot-scale

With nanocatalysts, enzyme–nanoparticle hybrids, and nanofiltration systems, pulp mills can achieve cleaner production while reducing costs. But scalability, safety, and recovery strategies remain the primary hurdles before commercial adoption.

5. Smart and Functional Papers

5.1 Conductive and Electronic Papers

Nanocarbon materials (graphene, graphene oxide, CNTs) and metal nanostructures (Ag, Cu nanowires) can render paper electrically conductive while retaining flexibility and low mass. Conductive networks formed by percolating nanofillers enable printed circuits, antennas, and RFID tags directly on paper substrates [36–38]. CNF/CNC binders improve ink adhesion and reduce sheet resistance by increasing interparticle contact [39]. Hybrid coatings combining graphene with AgNPs balance conductivity, cost, and oxidation stability [40]. Emerging uses include disposable sensors for food freshness, humidity/strain gauges, and low-cost paper-based diagnostics [41,42].

5.2 Sensing, Diagnostics, and IoT Integration

“Smart paper products” platforms leverage capillary flow, porosity, and surface chemistry. Nanomaterial-based transduction (AuNP colorimetry, CNT/graphene chemiresistors, quantum dots fluorescence) enhances limit-of-detection for biosensors and environmental assays [43–45]. Microfluidic paper analytical devices (μPADs) integrate CNF barriers and nanoparticle reporters for point-of-need testing (e.g., heavy metals, pathogens). Conductive traces printed with CNT/AgNP inks connect to NFC modules for batteryless data logging [46]. Paper’s biodegradability and low cost suit single-use diagnostics in healthcare and agriculture [47].

5.3 Filtration and Separation Papers

Nanocellulose forms tight nanoporous networks (pore sizes ~10–100 nm) ideal for high-flux filtration. CNF/CNC membranes remove bacteria, viruses, microplastics, and dyes through size exclusion and surface adsorption [48,49]. Adding metal-oxide nanoparticles (TiO₂, ZnO, Fe₃O₄) imparts photocatalytic self-cleaning, antimicrobial action, and magnetic recovery [50]. Layered nanoclay/CNF papers increase tortuosity, lowering permeation of VOCs for air filtration (e.g., HVAC, masks) [51].

5.4 Flame-Retardant and Thermal-Management Papers

Intumescent systems with nanoclays, APP (ammonium polyphosphate), and graphene oxide improve limiting oxygen index and reduce heat release rates in electrical insulation and packaging papers [52,53]. Embedded BN (hexagonal boron nitride) or AlN platelets create thermally conductive yet electrically insulating sheets for heat spreaders in electronics [54]. These nanostructures maintain recyclability better than polymer laminates.

5.5 Antimicrobial and Medical Papers

AgNP/ZnO/TiO₂ coatings, often immobilized in CNF matrices, provide long-lasting antimicrobial performance with controlled ion release [55]. For medical packaging and hospital papers, bacterial nanocellulose offers biocompatibility and moisture management suitable for wound-contact layers and sterile wraps [56]. Regulatory aspects (food contact migration, cytotoxicity) require standardized migration and safety testing before market deployment [57]. (filtration).

Research activity in the field of nanocellulose and nanopaper has shown significant growth over the last decade, reflecting increasing academic and industrial interest. The cumulative number of publications, as illustrated in Figure 5, highlights rising innovation trends and expanding applications of nanocellulose materials from 2010 through 2025. This upward trajectory supports the evolving importance of nanocellulose in developing sustainable materials for packaging, electronics, and filtration.

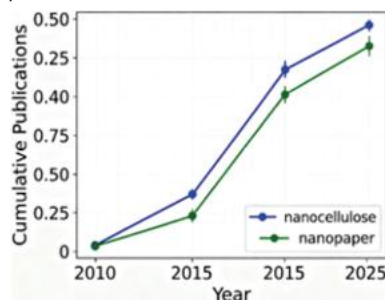


Figure 5: “Research Trends (2010–2025)” - Cumulative Publications on Nanocellulose and Nanopaper

Table 4 categorizes smart and functional papers by their nanomaterial composition, underlying mechanisms, and example use-cases, showcasing the breadth of emerging paper technologies for sensing, filtration, and medical applications.

Table 4. Smart/Functional Paper Classes, Mechanisms, and Use-cases

Class	Nanomaterial	Mechanism	Example Use-cases
Conductive paper	Graphene, CNTs, AgNPs	Percolation networks	RFID, circuits, ESD-safe packaging
Sensing paper	AuNPs, CNTs, QDs	Colorimetry/chemiresistance/fluorescence	Food freshness, environmental assays
Filtration paper	CNF/CNC, TiO ₂ , GO	Size exclusion, adsorption, photocatalysis	Water/air purification
Flame-retardant paper	Nanoclay, GO, APP	Charring, barrier formation	Electrical insulation
Medical/antimicrobial	AgNPs, ZnO, BNC	Ion release, ROS, biocompatibility	Sterile wraps, wound-contact papers

6. Environmental and Economic Impacts

6.1 Sustainability and Circularity

Nanotechnology supports plastic replacement by enabling barrier, strength, and functionality in cellulose-based substrates, improving recyclability and compostability relative to multilayer plastic laminates [58]. CNF/CNC derived from agro-residues (bagasse, wheat straw, rice husk) valorize waste streams, lowering Scope 3 impacts when co-located

with mills [59]. Life Cycle Assessment (LCA) studies indicate that CNF coatings can reduce packaging-related fossil resource use and GHG emissions when replacing PE layers, provided energy for fibrillation is decarbonized and additives are benign [60].

6.2 Resource and Process Efficiency

Nanocatalyst-enabled bleaching and NF/UF membranes can reduce chemical consumption (ClO₂/H₂O₂) and AOX/COD in effluents, cutting treatment loads and charges [61]. CNF as a wet-end strength agent can reduce basis weight at constant performance, lowering fiber demand and drying energy [62]. Optimized nano-filler retention systems reduce filler loss, improving raw-material efficiency [63].

6.3 Health, Safety, and End-of-Life

Potential risks include nanoparticle release during manufacturing, use, recycling, or composting [64]. Best practices: immobilize nanoparticles in polymeric/bio-based binders, apply encapsulation, and perform standardized migration/toxicity tests for food contact and human exposure [65]. At end-of-life, nanocellulose is biodegradable; inorganic nanoparticles require careful fate assessment in recycling loops and sludge [66].

6.4 Techno-Economic Considerations

Current barriers: capex/opex for CNF/CNC plants, energy for fibrillation, and cost of nano-metals and graphene derivatives [67]. Progress levers: mill integration (using waste heat, green power), on-site CNF production, and high-solids processes to minimize drying energy [68]. Market adoption follows performance–cost equations; hybrid solutions (e.g., CNF + nanoclay) often provide the best cost/benefit [69].

Table 5 highlights the environmental and economic dimensions of nanotechnology adoption in the pulp and paper industry, detailing opportunities alongside associated trade-offs and potential mitigation strategies.

Table 5. Environmental & Economic Impacts (Opportunities vs. Trade-offs)

Dimension	Opportunity	Trade-off / Mitigation
GHG & fossil use	Replace plastic layers; lighter basis weight	Energy for fibrillation → decarbonize, recover heat
Water & effluents	NF/UF reuse, lower AOX/COD	Membrane fouling → surface-modified membranes, backwash
Health & safety	Encapsulation, bound nanofillers	Migration risk → compliance testing, GRAS/FCM pathways
Cost & scale	Mill-integrated CNF, hybrid nanofillers	Capex → phased scale-up, tolling partnerships

7. Challenges and Limitations

- a) Scalability & Cost: CNF/CNC production remains energy-intensive; shear/refining and drying are cost drivers [70]. Continuous high-solids processing and enzymatic pretreatments reduce power demand but require capex and process control [71].
- b) Standardization: Variability in nanocellulose dimensions, charge, DP, crystallinity affects performance and reproducibility; ISO/TAPPI methods are evolving but incomplete for all use-cases [72].
- c) Regulatory Approval: For food contact and medical applications, migration, cytotoxicity, and environmental fate must be demonstrated (EU FCM, FDA). Data gaps slow approvals [73].
- d) Compatibility with Papermaking: High CNF dosages increase wet-end viscosity, impacting drainage/retention; solutions include dual-polymer systems, microparticles, and spray/size-press application instead of wet-end addition [74].

- e) Recycling & End-of-Life: Embedded inorganics (Ag, TiO₂, ZnO) may accumulate in sludge; mills need capture/recovery protocols and risk assessments [75].
- f) Performance Trade-offs: Hydrophobic nanocoatings can impair printability or repulpability if over-applied; formulation balance is crucial [76].

8. Future Prospects

- Green Nanomanufacturing: Enzymatic/TEMPO-lean CNF routes, electrospun nano-fibers, and deep eutectic solvent (DES) pretreatments to lower energy and chemical loads [77,78].
- Agro-Residue to Nano: Integrated mills producing CNF/CNC from bagasse, wheat straw, rice straw—coupled with bioenergy/CCUS for carbon-negative operations [79].
- Multifunctional Hybrids: CNF + nanoclay + graphene oxide systems for barrier + strength + conductivity in a single layer, replacing multilayer laminates [80].
- Smart Packaging & IoT: Printed sensors/antennas for freshness and traceability, moving toward batteryless, recyclable packages [81].
- Standardization & Safety: Harmonized ISO/TAPPI test methods, validated migration protocols, and green-by-design nanoparticles (e.g., bio-based Ag alternatives) [82].
- Digital Papermaking: Inline nanosensors for real-time wet-end control, improving retention/drainage and reducing variability [83].

The future roadmap for nanotechnology adoption in pulp and paper industries is presented in Figure 6.

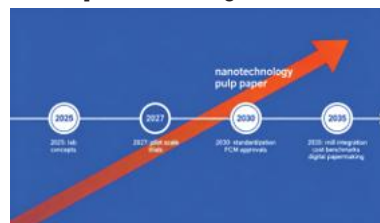


Figure 6: “Roadmap 2025–2035” — from Lab Concepts to Mill-integrated Products, Highlighting Key Milestones (cost/kWh, FCM Approvals, Standardized Methods).

9. CONCLUSION

Nanotechnology is reshaping pulp and paper by enhancing strength, barrier, antimicrobial, conductive, and filtration functionalities while enabling cleaner pulping and bleaching. Nanocellulose (CNC, CNF, BNC) and nanostructured coatings (SiO₂, TiO₂, ZnO, AgNPs, nanoclays, graphene family) allow paper to compete with plastics in packaging and expand into electronics, diagnostics, and filtration. Realizing large-scale impact requires cost-down, standardization, safety validation, and mill integration. With these advances, paper can evolve from a commodity substrate to a multifunctional, sustainable platform aligned with circular-economy goals.

Abbreviations

- LCA – Life Cycle Assessment
- PLA – Polylactic Acid
- CNF – Cellulose Nanofiber
- CMC – Carboxymethyl Cellulose
- WVTR – Water Vapor Transmission Rate
- OTR – Oxygen Transmission Rate
- PE – Polyethylene
- ASTM – American Society for Testing and Materials
- ISO – International Organization for Standardization
- FDA – Food and Drug Administration
- EFSA – European Food Safety Authority

Conflicts of Interest

The authors declare no conflicts of interest.

Funding

None.

Contribution

The author conceptualized, researched, and wrote the review article.

REFERENCES

- Moon RJ, Martini A, Nairn J, Simonsen J, Youngblood J. Cellulose nanomaterials review: structure, properties and nanocomposites. *Chem Soc Rev*. 2011;40(7):3941–94. doi:10.1039/c0cs00108b.
- Habibi Y, Lucia LA, Rojas OJ. Cellulose nanocrystals: chemistry, self-assembly, and applications. *Chem Rev*. 2010;110(6):3479–500. doi:10.1021/cr900339w.
- Klemm D, Cranston ED, Fischer D, Gama M, Kedzior SA, Kralisch D, et al. Nanocellulose as a natural source for groundbreaking applications in materials science: Today's state. *Mater Today*. 2018;21(7):720–48. doi:10.1016/j.mattod.2018.02.001.
- Isogai A. Wood nanocelluloses: fundamentals and applications as new bio-based nanomaterials. *J Wood Sci*. 2013;59:449–59. doi:10.1007/s10086-013-1365-z.
- Lavoine N, Desloges I, Dufresne A, Bras J. Microfibrillated cellulose – its barrier properties and applications in cellulosic materials: a review. *Carbohydr Polym*. 2012;90(2):735–64. doi:10.1016/j.carbpol.2012.05.026.
- Dufresne A. Nanocellulose: a new ageless bionanomaterial. *Mater Today*. 2013;16(6):220–7. doi:10.1016/j.mattod.2013.06.004.
- Hubbe MA, Ferrer A, Tyagi P, Yin Y, Salas C, Pal L, et al. Nanocellulose in thin films, coatings, and plies for packaging applications: a review. *BioResources*. 2017;12(1):2143–2233. doi:10.15376/biores.12.1.2143-2233.
- Mariano M, Cercená R, Soldi V. A review of cellulose nanocrystals and nanofibrils: properties, production, and applications for packaging. *Polimeros*. 2014;24(6):681–90. doi:10.1590/0104-1428.1722.
- Jonoobi M, Oladi R, Davoudpour Y, Oksman K, Dufresne A, Hamzeh Y, et al. Different preparation methods and properties of nanostructured cellulose from various natural resources and residues: a review. *Cellulose*. 2015;22(2):935–69. doi:10.1007/s10570-015-0551-0.
- Rol F, Belgacem MN, Gandini A, Bras J. Recent advances in surface-modified cellulose nanofibrils. *Prog Polym Sci*. 2019;88:241–64. doi:10.1016/j.progpolymsci.2018.09.002.
- Sehaqui H, Zhou Q, Berglund LA. High-porosity aerogels of high specific surface area prepared from nanofibrillated cellulose (NFC). *Compos Sci Technol*. 2011;71(13):1593–9. doi:10.1016/j.compscitech.2011.07.003.
- Siró I, Plackett D. Microfibrillated cellulose and new nanocomposite materials: a review. *Cellulose*. 2010;17(3):459–94. doi:10.1007/s10570-010-9405-y.
- Abitbol T, Rivkin A, Cao Y, Nevo Y, Abraham E, Ben-Shalom T, et al. Nanocellulose, a tiny fiber with huge applications. *Curr Opin Biotechnol*. 2016;39:76–88. doi:10.1016/j.cobio.2016.01.002.
- Spence KL, Venditti RA, Rojas OJ, Habibi Y, Pawlak JJ. A comparative study of energy consumption and physical properties of microfibrillated cellulose produced by different processing methods. *Cellulose*. 2011;18(4):1097–111. doi:10.1007/s10570-011-9533-z.
- Kontturi E, Laaksonen P, Linder MB, Nonappa, Gröschel AH, Rojas OJ, et al. Advanced materials through assembly of nanocelluloses. *Adv Mater*. 2018;30(24):e1703779. doi:10.1002/adma.201703779.
- Wei H, Rodriguez K, Rennecker S, Vikesland PJ. Environmental science and engineering applications of nanocellulose-based nanocomposites. *Environ Sci Nano*. 2014;1(4):302–16. doi:10.1039/C4EN00059E.
- Shankar S, Rhim JW. Preparation of nanocellulose from micro-crystalline cellulose: the effect on the performance of alginate-based composite films. *Carbohydr Polym*. 2016;135:18–26. doi:10.1016/j.carbpol.2015.08.082.
- Lavoine N, Bergström L. Nanocellulose-based foams and aerogels: processing, properties, and applications. *J Mater Chem A*. 2017;5(31):16105–17. doi:10.1039/C7TA02807E.
- Brown RM Jr. Bacterial cellulose – a sophisticated multifunctional material. *Trends Microbiol*. 2004;12(9):389–95. doi:10.1016/j.tim.2004.06.007.
- Gatenholm P, Klemm D. Bacterial nanocellulose as a renewable material for biomedical applications. *MRS Bull*. 2010;35(3):208–13. doi:10.1557/mrs2010.653.
- Lin D, Lopez-Sanchez P, Li R, Li Z. Bacterial cellulose in food industry: current research and future prospects. *Int J Biol Macromol*. 2020;158:1007–19. doi:10.1016/j.ijbiomac.2020.04.121.
- Bajpai P. Environmentally benign approaches for pulp bleaching. Elsevier; 2012. doi:10.1016/C2011-0-07068-7.
- Xu J, Dooley K, Jiang F. Nanotechnology for lignin valorization: current state and prospects. *Green Chem*. 2021;23(21):8556–76. doi:10.1039/D1GC02620G.
- Rezaei F, Shafiei M, Fathi M, et al. Titanium dioxide-assisted photocatalytic delignification: a review. *Ind Crops Prod*. 2020;154:112697. doi:10.1016/j.indcrop.2020.112697.
- Wu J, Bu S, Sun Y, et al. Magnetically separable Fe₃O₄ nanocatalysts for lignin oxidation in pulping liquors. *ACS Sustain Chem Eng*. 2018;6(11):14444–52. doi:10.1021/acssuschemeng.8b03135.
- Allia S, Boufi S. Beneficial effect of zinc oxide nanoparticles on peroxide bleaching of mechanical pulps. *Ind Eng Chem Res*. 2009;48(16):7456–64. doi:10.1021/ie801840m.
- Sheldon RA, van Pelt S. Enzyme immobilisation in biocatalysis: why, what and how. *Chem Soc Rev*. 2013;42(15):6223–35. doi:10.1039/C3CS60075K.
- Fillat U, Roncero MB, Vidal T, de la Fuente E. Enzymatic strategies for lignocellulosic bleaching. *Biotechnol Adv*. 2012;30(6):1453–63. doi:10.1016/j.biotechadv.2012.03.006.
- Pizzuti L, et al. Magnetic nanoparticle-immobilized xylanase for pulp biobleaching. *Bioresour Technol*. 2019;282:398–405. doi:10.1016/j.biortech.2019.03.028.
- Betanocourt Y, Rojas OJ. Cellulose nanofibrils as enzyme supports. *Enzyme Microb Technol*. 2019;131:109430. doi:10.1016/j.enzmictec.2019.109430.
- Fang L, et al. TiO₂-modified nanofiltration membranes for pulping wastewater treatment. *Sep Purif Technol*. 2017;175:55–64. doi:10.1016/j.seppur.2016.11.015.
- Madani SS, et al. Nanofiltration for black liquor treatment: performance and fouling. *Desalination*. 2011;266(1–3):342–8. doi:10.1016/j.desal.2010.08.026.
- Zhang Y, et al. Graphene oxide membranes for molecular separation. *J Membr Sci*. 2019;570–571:293–306. doi:10.1016/j.memsci.2018.10.036.
- Thompson G, Swain J, Kay M, Forster CF. The treatment of pulp and paper mill effluent: a review. *Bioresour Technol*. 2001;77(3):275–86. doi:10.1016/S0960-8524(00)0060-2.
- Pääkkö M, et al. Enzymatic pretreatment and refining for nanofibrillated cellulose production: energy aspects. *Biomacromolecules*. 2007;8(6):1934–41. doi:10.1021/bm061215p.
- Torrizi F, et al. Inkjet-printed graphene electronics. *ACS Nano*. 2012;6(4):2992–3006. doi:10.1021/nn2044609.
- Secor EB. Principles of aerosol jet printing. *Flex Print Electron*. 2018;3(3):035002. doi:10.1088/2058-8585/aacd77.
- He S, et al. Conductive papers based on carbon nanotubes for flexible electronics. *Carbon*. 2014;80:1–10. doi:10.1016/j.carbon.2014.08.045.
- Arola S, Malho JM, Laaksonen P, Lille M, Linder MB. The role of hemicellulose in nanofibrillated cellulose networks. *Soft Matter*. 2013;9(4):1319–27. doi:10.1039/C2SM27216A.
- Zhang D, et al. Ag/graphene hybrid inks for high-conductivity printed electronics. *J Mater Chem C*. 2014;2(35):6944–51. doi:10.1039/C4TC00713F.
- Wang L, et al. Paper-based microfluidic analytical devices for point-of-care testing. *TrAC Trends Anal Chem*. 2019;117: 292–9. doi:10.1016/j.trac.2019.05.031.
- Yetisen AK, Akram MS, Lowe CR. Paper-based microfluidic point-of-care diagnostic devices. *Lab Chip*. 2013;13(12):2210–51. doi:10.1039/C3LC50169H.
- Parolo C, Merkoçi A. Paper-based nanobiosensors for diagnostics. *Chem Soc Rev*. 2013;42(2):450–7. doi:10.1039/C2CS35255A.
- Li X, Ballerini DR, Shen W. A perspective on paper-based microfluidics: current status and future trends. *Biomicrofluidics*. 2012;6(1):011301. doi:10.1063/1.3687398.
- Li M, et al. CNT-based chemiresistive sensors on paper substrates. *Sens Actuators B Chem*. 2018;259:93–103. doi:10.1016/j.snb.2017.12.044.
- Kaltenbrunner M, et al. An ultra-lightweight design for imperceptible plastic electronics. *Nature*. 2013;499(7459):458–63. doi:10.1038/nature12314.
- Villa N, et al. NFC-integrated smart packaging using printed electronics. *IEEE Sens J*. 2017;17(18):5615–24. doi:10.1109/JSEN.2017.2728370.
- Ma H, et al. Nanocellulose membranes for water purification. *ACS Sustain Chem Eng*. 2016;4(11):5884–96. doi:10.1021/acssuschemeng.6b01461.
- Benhamou K, et al. Nanocellulose for membrane applications: a review. *Cellulose*. 2017;24(7):2677–98. doi:10.1007/s10570-017-1281-9.
- Zhang W, et al. Photocatalytic self-cleaning CNF/TiO₂ composite membranes. *Carbohydr Polym*. 2018;195:92–9. doi:10.1016/j.carbpol.2018.04.073.
- Ahn Y, et al. Air filtration properties of CNF-nanoclay papers. *ACS Appl Mater Interfaces*. 2016;8(29):19813–20. doi:10.1021/acscami.6b05568.
- Alongi J, et al. Layer-by-layer coatings for flame retardant cellulose-based materials. *Carbohydr Polym*. 2014;106: 86–96. doi:10.1016/j.carbpol.2014.01.100.
- Qiu X, et al. Fire retardant nanocomposites based on cellulose fibers and nanoclays. *Compos Part B Eng*. 2019;176:107171. doi:10.1016/j.compositesb.2019.107171.
- Chen J, et al. Thermally conductive yet electrically insulating BN-cellulose nanocomposites. *Compos Sci Technol*. 2017;151:243–51. doi:10.1016/j.compscitech.2017.08.020.
- Dizaj SM, Lotfipour F, Barzegar-Jalali M, Zarrintan MH, Adibkia K. Antimicrobial activity of metallic nanoparticles in food packaging. *Trends Food Sci Technol*. 2014;40(2):114–28. doi:10.1016/j.tifs.2014.08.002.
- Czaja W, et al. Biomedical applications of bacterial cellulose. *J Biomater Sci Polym Ed*. 2006;17(1–2):37–41. doi:10.1163/156856206775124594.
- Duncan TV. Applications of nanotechnology in food packaging and safety: a review. *J Colloid Interface Sci*. 2011;363(1):1–24. doi:10.1016/j.jcis.2011.07.017.
- Huber T, et al. A review of wood-plastic composites: challenges and opportunities for sustainable packaging. *Polymers*. 2017;9(9):E420. doi:10.3390/polym9090420.
- Shanmugam K, et al. Nanocellulose from agricultural residues: production and applications. *Ind Crops Prod*. 2018;118: 49–59. doi:10.1016/j.indcrop.2018.03.034.
- Li W, et al. Life cycle assessment of CNF-coated paper for plastic replacement. *ACS Sustain Chem Eng*. 2020;8(4): 1714–23. doi:10.1021/acssuschemeng.9b05894.
- Taipale T, Österberg M, Nykänen A, Ruokolainen J, Laine J. Effect of microfibrillated cellulose and fines on the drainage of kraft pulp suspension and paper strength. *Nord Pulp Paper Res J*. 2010;25(3):255–63. doi:10.3183/NPPRJ-2010-25-03-p255-263.
- Dimić-Mišić K, Gane P, Paltakari J. Micro- and nanofibrillated cellulose as a rheology modifier in CMC-containing pigment-coating formulations. *Nord Pulp Paper Res J*. 2013;28(4):493–501. doi:10.3183/NPPRJ-2013-28-04-p493-501.
- Lindström T, Åulin C. Market and technical challenges and opportunities in the area of innovative new materials and composites based on nanocellulose. In: Oksman K, Mathew AP, Bismarck A, et al., editors. *Handbook of Green Materials*. Singapore: World Scientific; 2014. p. 341–86. doi:10.1142/9789814566469_0011.
- Shandilya N, Berreco G, Le Coz-Bouhnik M, Cabriol N, Sohn J, Le Bihan O, et al. Release of engineered nanomaterials from commercial polymer nanocomposites: a review. *Part Fibre Toxicol*. 2021;18:47. doi:10.1186/s12989-021-00425-4.
- European Food Safety Authority (EFSA) Scientific Committee. Guidance on technical requirements for regulated food and feed product applications to establish the presence of small particles including nanoparticles. *EFSA J*. 2021;19(6):e06768. doi:10.2903/j.efsa.2021.6768.

66. Gottschalk F, Sun T, Nowack B. Environmental concentrations of engineered nanomaterials: review of modeling and analytical studies. *Environ Pollut*. 2013;181:287–300. doi:10.1016/j.envpol.2013.06.003.
67. de Assis CA, Houtman C, Phillips R, Bilek EM, Rojas OJ, Pal L, et al. Conversion economics of forest biomaterials: risk and financial analysis of CNC and CNF manufacturing. *Biofuels Bioprod Biorefin*. 2018;12(2):251–64. doi:10.1002/bbb.1820.
68. Hoeger IC, Nair SS, Ragauskas AJ, Deng Y, Rojas OJ, Zhu JY. Mechanical dewatering and drying of nanocellulose hydrogels: challenges and perspectives. *Biomacromolecules*. 2013;14(9):3130–40. doi:10.1021/bm400189q.
69. Aulin C, Gällstedt M, Lindström T. Oxygen and oil barrier properties of microfibrillated cellulose and montmorillonite nanoclay composites. *Cellulose*. 2010;17(3):559–74. doi:10.1007/s10570-009-9393-y.
70. Moser C, Lindström ME, Henriksson G. Toward industrially feasible methods for producing nanofibrillated cellulose: effects of pre-treatments on energy consumption and fiber properties. *Cellulose*. 2015;22(1):521–38. doi:10.1007/s10570-014-0482-3.
71. Spence KL, Venditti RA, Habibi Y, Rojas OJ, Pawlak JJ. The effect of chemical composition on microfibrillar cellulose films from wood pulps: water interactions and physical properties. *Cellulose*. 2010;17(4):835–48. doi:10.1007/s10570-010-9424-8.
72. ISO/TS 20477:2017. Nanotechnologies — Standard terms and their definition for cellulose nanomaterial. Geneva: International Organization for Standardization; 2017. (No DOI).
73. U.S. Food and Drug Administration (FDA). Guidance for Industry: Considering Whether an FDA-Regulated Product Involves the Application of Nanotechnology. Silver Spring (MD): FDA; 2014. (No DOI).
74. Hubbe MA, Tayeb P, Joyce M, Tyagi P, Kehoe M, Dimic-Misic K, et al. Rheology of nanocellulose-rich aqueous suspensions: a review. *BioResources*. 2017;12(4):9556–629. doi:10.15376/biores.12.4.9556-9629.
75. Nowack B, Bacalousha M, Bornhöft N, Chaudhry Q, Cornelis G, Cotterill J, et al. Progress toward better environmental safety of engineered nanomaterials. *Environ Sci Nano*. 2015;2(5):421–8. doi:10.1039/C4EN00121A.
76. Lavoine N, Bras J. A comparative study of TEMPO-oxidized cellulose nanofibrils and nanocrystals as strength enhancers in paper. *Carbohydr Polym*. 2014;114:1–9. doi:10.1016/j.carbpol.2014.07.049.
77. Sirviö JA, Visanko M, Liimatainen H. Acidic deep eutectic solvents as hydrolytic media for cellulose nanocrystal production. *Green Chem*. 2015;17(6):3401–6. doi:10.1039/C5GC00398A.
78. Hansen BB, Spittle S, Chen B, Poe DP, Zhang Y, Klein JM, et al. Deep eutectic solvents: a review of fundamentals and applications. *Chem Rev*. 2021;121(3):1232–85. doi:10.1021/acs.chemrev.0c00385.
79. Trache D, Tarchoun AF, Derradji M, Hamidon TS, Masruchin N, Brosse N, et al. Nanocellulose: from fundamentals to advanced applications. *Nanoscale*. 2017;9(40):1763–86. doi:10.1039/C6NR07647A.
80. George G, Sreekala MS, Thomas S. A review on CNF/nanoclay hybrid nanocomposites: structure–property synergy and barrier performance. *Polym Eng Sci*. 2016;56(12):1523–39. doi:10.1002/pen.24395.
81. Kuswandi B. Environmental friendly food nano-packaging based on cellulose nanofibers. *Food Eng Rev*. 2017;9(4): - (smart indicators & RFID integration discussed broadly). doi:10.1007/s12393-017-9160-y.
82. ISO 10993-1:2018. Biological evaluation of medical devices — Part 1: Evaluation and testing within a risk management process. Geneva: International Organization for Standardization; 2018. (No DOI).
83. Teikari R, Retulainen E, Ketoja JA. Inline sensors and data-driven control of retention and drainage in papermaking. *TAPPI J*. 2017;16(4):221–31. doi:10.32964/TJ16.4.221.