



HISTOLOGICAL STUDY TO COMPARE THE APPROPRIATE PARTICLE SIZE OF BETA TCP FOR SOCKET PRESERVATION

Oral Pathology

Lanka Mahesh*

Private Practice, New Delhi, India. *Corresponding Author

José Luis Calvo-Guirado

Associate Researcher Universidad Autónoma de Chile, Private Practice Murcia Spain.

Sagrika Shukla

Private Practice, New Delhi, India.

Anshi Jain

Reader, Department of Oral Pathology, ITS Dental College, Ghaziabad, UP, India.

ABSTRACT

Background: One the most used and potent synthetic bone graft substitute which is not only osteoconductive, but also osteoinductive which has been recently discovered and gain popularity is the β -tricalcium phosphate (β -TCP). Along with its cell-mediated resorption property β -TCP allow regeneration of full bone defect. Its clinical outcome is sometimes considered to be "unpredictable", possibly due to a poor understanding of β -TCP physico-chemical properties. **AIM:** Histological evaluation and effects of β -TCP small and large particle at the site of defect in cases of grossly decayed teeth, bone defect and other required areas. **Material and Methods:** Total of 20 cases were included in the study (10 cases each of small and large particle). Trephine biopsy was performed and sent for histological evaluation. **Results:** Histological evaluation depicted the results on the basis of new bone formation with residual bone graft material. Vascularity is studied in both the cases with areas of inflammation. **Conclusion:** Production of Mesenchymal stem cells progenitors plays a potent role in elucidating the effects of small β -TCP particle and is responsible for the production of new bone.

KEYWORDS

Bone graft, particle size, tooth extraction, alveolar volume loss

INTRODUCTION:

Replacement of natural missing teeth with an implant has become a routine procedure in dentistry, with only one pre-requisite, which is, presence of enough bone at the surgical site to place an implant which can restore function and aesthetics. Autogenous bone is the gold standard due to its osteogenic, osteoinductive and osteoconductive properties, however its limited availability, very fast resorption and additional surgical site has decreased its rampant usage¹. Also, other types of graft materials, such as xenograft and alloplasts have become popular due to their easy availability and reliable results. However, when it comes to predictable regeneration there are many factors one must consider, one being the particle size of the graft used, though not a widely studies topic, does play an important role in bone turnover.

The right kind of particle size has since long been in discussion. Mowlem way back in 1944 suggested that small particle size of the autogenous cancellous bone graft may enhance osteogenic effect². Robinson also noted enhanced Osteogenesis, but also hypothesized that small particles in the bone Coagulum would resorb more readily³. Usually, when a bone crusher is used to grind large chunks of autogenous bone collected intraorally, it produces small particle size⁴. In the literature, particle size of 100- 400 μ m has been found to be most appropriate^{5,6}. It was suggested that these small particles may enhance osteogenesis compared to larger particles (1000 - 2000 μ m) due to enlarged surface area and ideal pore size between particles which allow for increased vascularization and osteogenesis to occur. Particles smaller than the aforementioned size get resorbed too fast for bone formation to occur. Particles that are too large may hinder vascularization and may be sequestered⁷.

But recent research showed that large particle size (1000-2000 μ m) when used for lateral ridge augmentation resulted in greater ridge width gain at the level of the crest, however, vital bone formation was more extensive when small particles (250-1000 μ m) were used⁸. To study the particle size in this study authors chose a synthetic bone graft, β -TCP, it being synthetic in nature, demonstrates osteoconduction, osteoinduction, and cell-mediated resorption. It has also been used as a carrier for local administration of drugs (bone morphogenic proteins, antibiotics) at the defect site. Interestingly, with β -TCP there is production of more bone when the osteoclastic activity is more⁹. And the calcium released during resorption is used up for more bone formation¹⁰. Some of β -TCP has also shown osteoinductive activity¹¹⁻¹³, but for that to happen the graft should be first autoclaved. According to Kühlet al¹⁴ there was no difference between autogenous bone alone or in combination with β -TCP while new bone formation was concerned. In this study, two different sizes were used, 0.25-1 small particle size and 1-2 large particle size.

MATERIAL AND METHODS

All patients undergoing bone grafting followed by implant placement were counselled and only the cooperative patients were enrolled for the study. The following were the inclusion criterias:

1. Above 25 years of age.
2. Deficient bone, grossly destructed tooth, or any other indication for dental implant.
3. Patients with controlled medical conditions such as diabetes, etc.
4. Not allergic to any of the bio-materials used in the study.
5. Compliant towards the study.

Exclusion Criteria:

1. Patients with systemic diseases and/or presence of infections contraindicating periodontal surgery/implant placement.
2. Patients on medication known to interfere with tissue health and healing.
3. Pregnant or lactating females.
4. Patients with known habit of smoking and tobacco chewing.
5. Patients allergic to any product or to any of the medications used in the study.

After complete medical and dental evaluation, patients were randomly divided into large and small particles groups:

Group I: large particles, 10 cases each

Group II: small particles, 10 cases each

Procedure:

The surgical procedure was done following all aseptic norms of the surgery, any grossly destructed teeth requiring implant was extracted and socket preservation was done using powerbone (bone graft) powerbone TURKEY. The socket was covered with a collagen plug, and sutures were placed to keep the collagen plug in place. (Patient was prescribed with mouthwash, Bluem, Holland)

Sutures were removed after 10 days and the healing was uneventful. By 4 months, at the time of implant placement, bone core was taken with a trephine bur of size 3.2mm for the histological examination and the implant fixture was placed at the same surgical visit

Histological Evaluation:

Histopathology of (large) size 1-2 mm bone graft particle

METHODOLOGY:

3.2 mm trephine core biopsies were obtained and fixed immediately in

neutral buffered formalin solution for 24-48 hours. The specimens were processed after decalcifying in mild decalcifying agent (10% EDTA, pH 7.4). The tissues were processed using standard tissue processing laboratory protocol of dehydration, clearing and infiltration with paraffin wax. Embedding and tissue block preparation was done with paraffin wax. 4 micron thick sections were stained with Hematoxylin and Eosin stains. The slides thus obtained were viewed in research microscope (Olympus BX53) and digital images were captured in low and high magnification (Olympus EPL3).

Methodology for small size graft particle: 0.25-1mm

3.2mm trephine core biopsies were obtained and fixed immediately in neutral buffered formalin solution for 24-48 hours. The specimens were processed after decalcifying in mild decalcifying agent (10% EDTA, pH 7.4). The tissues were processed using standard tissue processing laboratory protocol of dehydration, clearing and infiltration with paraffin wax. Embedding and tissue block preparation was done with paraffin wax. 4 micron thick sections were stained with Hematoxylin and Eosin stains. The slides thus obtained were viewed in research microscope (Olympus BX53) and digital images were captured in low and high magnification (Olympus EPL3).

RESULTS:

Since Bone is not completely inorganic in nature is 65% inorganic and 35% organic various stages of mineralization can be appreciated under Microscopic analysis. Decalcification procedure is used to study the relationship of soft and hard tissue together. Therefore submitted decalcified section of large beta TCP particle was stained with standard Hematoxylin and Eosin stain and showed well formed areas of mineralized bone with cellular components composed of osteoblasts, osteocytes, osteoid and vascular connective tissue. Abundant areas of mature bone formation with varying degrees of mineralization within a fibrocellular connective tissue stroma with minimal residues of remnant graft material were evident. The mature bone showed lamellations, lined by bone lining cells and entrapped osteocytes with in the osteocytic lacunae. These sections also showed focal areas showing residual graft particle at the graft- new bone interface. Very mild diffuse inflammatory infiltrate was seen suggesting satisfactory uptake of the grafted biomaterial in the absence of remarkable host inflammatory reaction. Areas showing new bone formation with entrapped osteocytes within the osteocytic lacunae at higher magnification were also seen. Vascularity and areas of new blood vessel formation is not appreciated in the histology of the section.

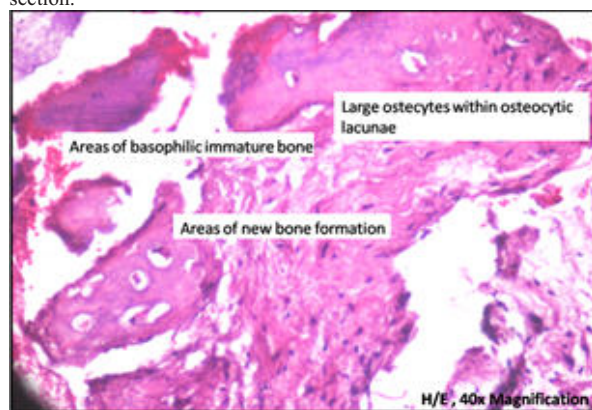


Figure 1. Hematoxylin and Eosin stained section of Large Beta TCP particle with areas of new bone formation with areas of no new blood vessel formation. (40x magnification)

For Small Bone Graft Particles

The Hematoxylin and Eosin stained section showed well formed areas of Bony Trabeculae with varying stages of Mineralization. Section showed abundant areas of basophilic immature bony trabeculae with large number of entrapped osteocytes lined by osteoblastic rimming and vascular connective tissue. Focal areas showed the presence of new bone formation and areas of remnant graft material at the graft-new bone interface. The mature bone showed lamellations, lined by bone lining cells and entrapped osteocytes with in the osteocytic lacunae. Dense infiltration of diffuse inflammatory infiltrate was seen suggesting satisfactory uptake of the grafted biomaterial. Vascularity and areas of new blood vessel formation is

appreciated in the histology of the section

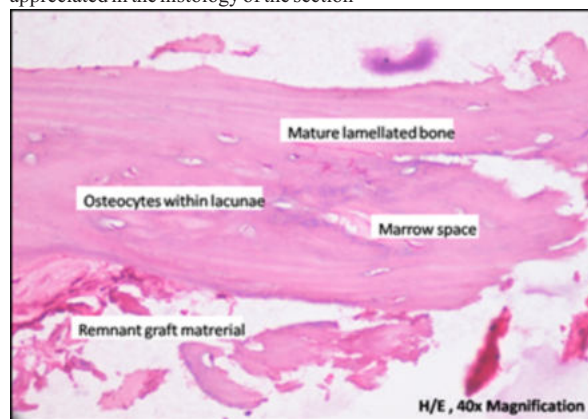


Figure 2: Hematoxylin and eosin stained section of small particle Beta TCP showing areas of new bone formation and areas of vascularity and inflammatory infiltrate. (40x magnification)

DISCUSSION:

In one of the early discussions on bone augmentation, Rivault¹⁵ stated that, as a rule, the graft particles get resorbed and then replaced by a new mineralized tissue along the walls of living host tissue, showing that 'host cellular elements' were more important than the graft material used, which only provides mineral salts, hence lies the importance of particle size³. This statement cannot be considered correct when it comes to autogenous bone as it is osteoinductive, osteogenic and osteoconductive, but due to aforementioned disadvantages its use has decreased. But when a different graft material is being used for augmentation then the intrinsic property of the graft type must be considered in selecting large or small particle size.

Allografts, are readily available but, they do not produce the inorganic calcium or scaffolding necessary for bone regeneration but provide excellent source of collagen type I¹⁶. so, even if large particles are used for bone regeneration, it will produce predictable results. A study found that even the farthest particles of freeze-dried bone allograft from the host-graft interface were embedded in new bone¹⁷. In 2010, Chackartchi et al¹⁸ found no clinical or histological differences between the small and large particle size of DBBM. Similar results were observed by Pereyra et al¹⁹, high rate of bone formation was observed regardless of the particle size Bio-Oss® S (0.25-1 mm) and Bio-Oss L (1-2 mm). Fucini et al²⁰ too noted that results did not differ significantly when particles 250 to 500 µm or 850 to 1000 µm were used to treat periodontal defects. Xenograft, on the other hand lacks organic component, inorganically provide a natural architectural matrix as well as a high source of calcium²¹ and also, helps in maintaining the physical dimensions of the augmented bone during the remodeling phases²². One must also consider resorption rate of xenograft, in a study by Degidi et al²³ even after 8 years of placement of bovine bone, 6.2% of the xenograft could be found at the site and in another study 17.3% of the graft even after 11 years of its placement²⁴. Hence, in author's opinion, a small particle size should be considered when using a xenograft, this however, has not been confirmed in any of the clinical trials or histological studies, only observations/small case series/animal studies happen to highlight²⁵. In a study comparing two different particle sizes of demineralized bovine bone mineral (DBBM) for sinus floor augmentation, authors stated that both the sizes act similarly when it comes to new bone formation²⁶. When it comes to allografts, large particles are suggested for lateral ridge augmentation²⁷. Hall et al²⁸ compared two different size range bioactive glass, 300 to 355 microns and other one with large size range 90 to 710 microns with demineralized freeze-dried bone allograft and stated that size of the graft particle is not significant. His results showed higher percent bone-to-implant contact and percent bone height fill in with the use of DFDBA.

For osteoconduction to occur, presence of differentiated mesenchymal cells becomes paramount^{29,30}. This can be made possible by maintaining adequate blood supply. In the histology of large bone particles, we cannot appreciate vascularity, as much as it can be appreciated in the histology of small graft particles. Small particle size means more surface area, facilitating growth factors to form new blood vessels and accelerating differentiation of mesenchymal cells into

osteoblasts³¹. Another thing to be understood is the fact that in all the studies aforementioned authors have used different graft type for regeneration of different bone at different sites, this shows that different bone particles exhibit different bone healing abilities which is also site dependant. However, there is no literature with large case series, studying one type of bone graft in different sites to state which particle size is suitable for which site for regeneration³²⁻³⁵.

Another pointer to ponder upon in achieving vascularization is the space between graft particles, which should be more than 100 μm ^{36,37}. Research has shown that there is greater bone formation when there is spaces of 300 to 500 μm between particles as compared to 50 to 100 μm of space^{38,39}. This depends upon the porous structure of the graft particle and was found to be a significant factor in osteoconduction and synostosis^{40,41}. Studies have demonstrated that materials with high porosity have a positive impact on bone formation⁴². In literature, two different pore sizes, <5 μm in diameter and >100 μm in diameter have been studied⁴³. Micropores tend to increase the surface area of the graft while macropores tend to enhance material resorption and boost osteoinduction⁴⁴. Presence of open and interconnected macropores are vital for blood vessel formation, cell migration, diffusion of nutrients, and circulation of pro-osteogenic factors⁴⁵. β -TCP scaffolds with interconnected pore structure (ihTCP) presents higher new bone formation volume⁴⁶. β -TCP being a porous graft material, has the ability to boost the infiltration of MSCs, thus enhancing new bone formation⁴⁷. In an experimental study while comparing porosity between β -TCP blocks with $58.1 \pm 1.7\%$ porosity and dense β -TCP blocks group with 10.9 ± 2.3 porosity, former showed 200-fold higher new bone formation just in 4 weeks⁴⁸. This shows that particle size and a porous structure are crucial for new bone formation, however the porous structure is dependent upon the particle size.

Literature also suggests use of large particle size, Urist et al⁴⁹ reported that particles size of 1000 to 2000 μm were more effective in bone formation, whereas, smaller size of 250 to 420 μm interrupted chondrogenesis and ossification. Another author Cornu et al⁵⁰ stated that large particles of fresh-frozen bone have higher stiffness than smaller morsels during impaction. Our study is in consistency with the literature which states that small particle size enhances bone regeneration.

CONCLUSION:

Macrophages are vital regulators of skeletal remodeling and osseous repair. Based on histological study it is safe to state that small particles size aids in production of more number of residents MSC's which further leads to more vascularisation with osteogenic differentiation, hence more bone formation. Therefore it has been putforth that bone osteogenesis initiated by MSCs with artificial bone may create a perfect combination, and make artificial bone a better scaffold with potential of osteoconduction and osteoinduction.

Acknowledgement: none

Conflict Of Interest: none

REFERENCES

- Jensen SS, Bosshardt DD, Buser D. (2009). Bone Grafts and Bone Substitute Materials. In: Danielbuser, Guided Bone Regeneration, 2Eds., Hanover Park IL, Quintessence, 71-96.
- Mowlem R. (1944). Cancellous chip bone grafts: Report of 75 cases. *Lancet* 2:746-748. [DOI.org/10.1016/S0140-6736\(00\)74285-1](https://doi.org/10.1016/S0140-6736(00)74285-1).
- Robinson RE. (1969). Osseous coagulum for bone induction. *J Periodontol* 40:503-10. [doi: 10.1902/jop.1969.40.9.503](https://doi.org/10.1902/jop.1969.40.9.503).
- Diem CR, Bowers GM, Moffitt WC. (1972) Bone blending: a technique for osseous implants. *J Periodontol* 43: 295-7. [doi: 10.1902/jop.1972.43.5.295](https://doi.org/10.1902/jop.1972.43.5.295).
- Zaner DJ, Yukna RA. (1984) Particle size of periodontal bone grafting materials. *J Periodontol* 55:406-9. [doi: 10.1902/jop.1984.55.7.406](https://doi.org/10.1902/jop.1984.55.7.406).
- Shapoff CA, Bowers GM, Levy B, et al. (1980) The effect of particle size on the osteogenic activity of composite grafts of allogeneic freeze-dried bone and autogenous marrow. *J Periodontol* 51: 625-30. [doi: 10.1902/jop.1980.51.11.625](https://doi.org/10.1902/jop.1980.51.11.625).
- Committee on Research, Science and Therapy of the American Academy of Periodontology. Tissue banking of bone allografts used in periodontal regeneration. *J Periodontol* 2001;72:834-8. [doi: 10.1902/jop.2001.72.6.834](https://doi.org/10.1902/jop.2001.72.6.834).
- Basma HS, Saleh MHA, Geurs NC, et al. (2022). The effect of bone particle size on the histomorphometric and clinical outcomes following lateral ridge augmentation procedures. A randomized double blinded controlled trial. *J Periodontol*. Epub ahead of print. [doi: 10.1002/JPER.22-0212](https://doi.org/10.1002/JPER.22-0212).
- Tanaka T, Saito M, Chazono M, et al. (2010). Effects of alendronate on bone formation and osteoclastic resorption after implantation of beta-tricalciumphosphate. *J Biomed Mater Res Part A*. 93:469–474. [doi: 10.1002/jbm.a.32560](https://doi.org/10.1002/jbm.a.32560).
- Le Huec JC, Clément D, Brouillaud B, et al. (1998). Evolution of the local calcium content around irradiated β -tricalcium phosphate ceramic implants: In-vivo study in the rabbit. *Biomaterials*. 19:733–738. [doi: 10.1016/s0142-9612\(97\)00189-0](https://doi.org/10.1016/s0142-9612(97)00189-0).
- Kondo N, Ogose A, Tokunaga K, et al. (2006) Osteoinduction with highly purified beta-tricalcium phosphate in dog dorsals and the proliferation of osteoblasts before heterotopic bone formation. *Biomaterials*. 27:4419–4427. [doi: 10.1016/j.biomaterials.2006.04.016](https://doi.org/10.1016/j.biomaterials.2006.04.016).
- Nasu T, Takemoto M, Akiyama N, et al. (2009). EP4 agonist accelerates osteoinduction and degradation of P-tricalcium phosphate by stimulating osteoclastogenesis. *J Biomed Mater Res - Part A*. 89:601–608. [doi: 10.1002/jbm.a.31984](https://doi.org/10.1002/jbm.a.31984).
- Davison NL, Gamblin AL, Layrolle P. (2014). Liposomal clodronate inhibition of osteoclastogenesis and osteoinduction by submicrostructured beta-tricalcium phosphate. *Biomaterials*. (2014). [doi: 10.1016/j.biomaterials.2014.03.013](https://doi.org/10.1016/j.biomaterials.2014.03.013).
- Kühl, S, Brochhausen C, Götz H, et al. (2013). Influence of bone substitute materials on the bone volume after maxillary sinus augmentation: a microcomputerized tomography study. *Clin. Oral. Invest.* 17:543–551. [doi: 10.1007/s00784-012-0732-2](https://doi.org/10.1007/s00784-012-0732-2).
- Rivault AF, Toto PD, Levy S, et al. (1971) Autogenous bone grafts, osseous coagulum and osseous retrograde procedures in primates. *J Periodontol* 42: 787, 1971. [doi: 10.1902/jop.1971.42.12.787](https://doi.org/10.1902/jop.1971.42.12.787).
- Hoexter DL. (2002) Bone regeneration graft materials. *J Oral Implantol*. 28:290–294. [doi: 10.1563/1548-1336\(2002\)028<0290:BRGM>2.3.CO;2](https://doi.org/10.1563/1548-1336(2002)028<0290:BRGM>2.3.CO;2).
- Piattelli A, Scarano A, Corigliano M, et al. (1996) Comparison of bone regeneration with the use of mineralized and demineralized freeze-dried bone allografts: a histological and histochemical study in man. *Biomaterials*. 17:1127–1131. [doi: 10.1016/0142-9612\(96\)85915-1](https://doi.org/10.1016/0142-9612(96)85915-1).
- Chackartchi T, Iezzi G, Goldstein M, et al. (2011). Sinus floor augmentation using large (1–2 mm) or small (0.25–1 mm) bovine bone mineral particles: a prospective, intra-individual controlled clinical, micro-computerized tomography and histomorphometric study. *Clin Oral Implant Res*. 22:473–480. [doi: 10.1111/j.1600-0501.2010.02032.x](https://doi.org/10.1111/j.1600-0501.2010.02032.x).
- de Molon RS, Magalhaes-Tunes FS, Semedo CV, et al. (2019). A randomized clinical trial evaluating maxillary sinus augmentation with different particle sizes of demineralized bovine bone mineral: histological and immunohistochemical analysis. *Int J Oral Maxillofac Surg*. 48:810–823. [doi: 10.1016/j.ijom.2018.09.003](https://doi.org/10.1016/j.ijom.2018.09.003).
- Fucini SE, Quintero G, Gher ME, et al. (1993) Small versus large particles of DFDBs in human intrabony periodontal defects. *J Periodontol* 64:844–847. [doi: 10.1902/jop.1993.64.9.844](https://doi.org/10.1902/jop.1993.64.9.844).
- Callan DP, Rohrer MD. (1993) Use of bovine-derived hydroxyapatite in the treatment of edentulous ridge defects: a human clinical and histologic case report. *J Periodontol* 64:575–582. [doi: 10.1902/jop.1993.64.6.575](https://doi.org/10.1902/jop.1993.64.6.575).
- Misch CE, Dietrich F. (1993) Bone grafting materials in implant dentistry. *Implant Dent*. 2(3):158–167. [doi: 10.1097/00008505-199309000-00003](https://doi.org/10.1097/00008505-199309000-00003).
- Degidi M, Perrotti V, Piattelli A, et al. (2013). Eight-year results of site retention of anorganic bovine bone and anorganic bovine matrix. *J Oral Implantol*. 39:727–732. [doi: 10.1563/AAID-JOI-D-11-00091](https://doi.org/10.1563/AAID-JOI-D-11-00091).
- Shanbhag S, Shanbhag V, Stavropoulos A. (2014) Volume changes of maxillary sinus augmentations over time: a systematic review. *Int J Oral Maxillofac Implants*. 29:881–892. [doi: 10.11607/jomi.3472](https://doi.org/10.11607/jomi.3472).
- Aghaloo TL, Moy PK. (2007). Which hard tissue augmentation techniques are the most successful in furnishing bony support for implant placement? *Int J Oral Maxillofac Implants*. 22 (Suppl):49-70. PMID: 18437791.
- Testori T, Wallace SS, Trisi P, et al. (2013) Effect of xenograft (ABBM) particle size on vital bone formation following maxillary sinus augmentation: a multicenter, randomized, controlled, clinical histomorphometric trial. *Int J Periodontics Restorative Dent* 33:467–475. [doi: 10.11607/jopr.1423](https://doi.org/10.11607/jopr.1423).
- Kheir MG, Kheir S, Lakha T. (2018) Does Graft Particle Type and Size Affect Ridge Dimensional Changes After Alveolar Ridge Split Procedure? *J Oral Maxillofac Surg* 76:761–769. <https://doi.org/10.1016/j.joms.2017.11.002>.
- Hall EE, Meffert RM, Hermann JS, et al. (1999) Comparison of bioactive glass to DFDB in the treatment of intrabony defects around implants in the canine mandible. *J Periodontol* 70:526–535. [doi: 10.1902/jop.1999.70.5.526](https://doi.org/10.1902/jop.1999.70.5.526).
- Mulliken JB, Glowacki J. (1980) Induced osteogenesis for repair and construction in the craniofacial region. *Plast Reconstr Surg* 65:553–560. [doi: 10.1097/00006534-198005000-00001](https://doi.org/10.1097/00006534-198005000-00001).
- Elasalanty ME, Genecov DG. (2009) Bone grafts in craniofacial surgery. *Cranio maxillofac Trauma Reconstr*. 2:125–34. [doi: 10.1055/s-0029-1215875](https://doi.org/10.1055/s-0029-1215875).
- Nam JW, Kim MY, Han SJ. (2016). Cranial bone regeneration according to different particle sizes and densities of demineralized dentin matrix in the rabbit model. *Maxillofac Plast Reconstr Surg*. 38:27. [doi: 10.1186/s40902-016-0073-1](https://doi.org/10.1186/s40902-016-0073-1).
- Shirotu T, Ohno K, Motohashi M, et al. (1996) Histologic and microradiologic comparison of block and particulate cancellous bone and marrow grafts in reconstructed mandibles being considered for dental implant placement. *J Oral Maxillofac Surg* 54:15–20. [doi: 10.1016/s0278-2391\(96\)90294-3](https://doi.org/10.1016/s0278-2391(96)90294-3).
- Isaksson S, Alberius P, Klinge B. (1992) Contribution of autogenic membranous bone chips and bone paste to healing of rabbit skull defects. *Scand J Dent Res* 100:274–278. [doi: 10.1111/j.1600-0722.1992.tb01070.x](https://doi.org/10.1111/j.1600-0722.1992.tb01070.x).
- Fonseca RJ, Clark PJ, Burkner EJ, et al. (1980) Revascularization and healing of onlay particulate autologous bone grafts in primates. *J Oral Maxillofac Surg* 38:572–577. PMID: 6156232.
- Nweke CE, Stegemann JP. Fabrication and osteogenic function of progenitor cell laden gelatin microcarriers. *J Biomed Mater Res B Appl Biomater*. 2022 Jun;110(6):1265–1278.
- Klawitter JJ, Hulbert SF (1971) Application of porous ceramics for the attachment of load bearing internal orthopedic application. *J Biomed Master Res Sympos* 2:161. <https://doi.org/10.1002/jbm.820050613>.
- Pederson KN, Haanaes HR, Lyng S. (1974) Tissue ingrowth into mandibular intrabony porous ceramic implants. *Int J Oral Surg* 3:158. [doi: 10.1016/s0300-9785\(74\)80020-7](https://doi.org/10.1016/s0300-9785(74)80020-7).
- Chang BS, Lee CK, Hong KS. (2000) Osteoconduction at porous hydroxyapatite with various pore configurations. *Biomaterials* 21:1291–1298. [doi: 10.1016/S0142-9612\(00\)00030-2](https://doi.org/10.1016/S0142-9612(00)00030-2).
- Flautre B, Descamps M, Delecourt C. (2001) Porous HA ceramic for bone replacement: role of the pores and interconnections experimental study in the rabbit. *J Mater Sci Mater Med*. 12:679–682. [doi: 10.1023/a:1011256107282](https://doi.org/10.1023/a:1011256107282).
- Akazawa T, Murata M, Sasaki T. (2006) Biodegradation and bioabsorption innovation of the functionally graded bovine bone oriented apatite with blood permeability. *J Biomed Mater Res*. 76:44–51. [doi: 10.1002/jbm.a.30439](https://doi.org/10.1002/jbm.a.30439).
- Tamai N, Myoui A, Tomita T. (2002) Novel hydroxyapatite ceramics with an interconnective porous structure exhibit superior osteoconduction in vivo. *J Biomed Mater Res*. 59:110–111. [doi: 10.1002/jbm.1222](https://doi.org/10.1002/jbm.1222).
- Raeisdasteh Hokmabad V, Davaran S, Ramazani A, et al. (2017). Salehi R. Design and fabrication of porous biodegradable scaffolds: a strategy for tissue engineering. *J Biomater Sci Polym Ed*. 28:1797–1825. [doi: 10.1080/09205063.2017.1354674](https://doi.org/10.1080/09205063.2017.1354674).
- Blokhuys TJ, Termaat MF, den Boer FC, et al. (2000). Properties of Calcium Phosphate Ceramics in Relation to Their In Vivo Behavior. *J Trauma* 48:179–186. [doi: 10.1097/00005373-200001000-00037](https://doi.org/10.1097/00005373-200001000-00037).
- Davison NL, Luo X, Schoenmaker T, et al. (2014). Submicron-scale Surface Architecture of Tricalcium Phosphate Directs Osteogenesis In Vitro and In Vivo. *Eur Cell Mater*. 27:281–297. [doi: 10.22203/escm.v027a20](https://doi.org/10.22203/escm.v027a20).
- Loh QL, Choong C. (2013). Three-dimensional Scaffolds for Tissue Engineering Applications: Role of Porosity and Pore Size. *Tissue Eng Part B, Rev*. 19:485–502. [doi: 10.1089/ten.TEB.2012.0437](https://doi.org/10.1089/ten.TEB.2012.0437).
- Lu T, Feng S, He F, et al. (2020). Enhanced Osteogenesis of Honeycomb β -tricalcium

- Phosphate Scaffold by Construction of Interconnected Pore Structure: An In vivo Study. J Biomed Mater Res Part A. 108:645–653. doi: 10.1002/jbma.a.36844.
47. Karageorgiou V, Kaplan D. (2005). Porosity of 3D Biomaterial Scaffolds and Osteogenesis. *Biomaterials* 26:5474–5491. doi: 10.1016/j.biomaterials.2005.02.002.
 48. Putri TS, Hayashi K, Ishikawa K. (2020). Bone Regeneration Using BetaTricalcium Phosphate (Beta-TCP) Block with Interconnected Pores Made by Setting Reaction of Beta-TCP Granules. *J Biomed Mater Res Part A*. 108:625–632. doi: 10.1002/jbma.a.36842.
 49. Urist, MR, Silverman BF, Buring K, et al. (1967). The bone induction principle. *Clin Orthop Relat Res*. 53:243–83. PMID: 4870495.
 50. Cornu O, Schubert T, Libouton X et al. (2009) Particle size influence in an impaction bone grafting model. Comparison of fresh-frozen and freeze-dried allografts. *J Biomechanics*. 42:2238–2242. doi:10.1016/j.jbiomech.2009.06.045.